


LARP

TQS

Status and Plan


Helene Felice



LARP

TQS Tests

| Magnet | Conductor | Coils | Island | Temperature | Test |
|--------|--|-----------------------|----------|---------------|--------------------------------|
| TQS01a | MJR 54/61 (1900 A/mm ²) | 5, 6, 7, 8 | Bronze | 4.4 K | April 2006 LBNL |
| TQS01b | MJR 54/61 | 14, 15, 7, 8 | Bronze | 4.4 K | Nov, 2006 LBNL |
| TQS01c | MJR 54/61 | 5, 15, 7, 8 | Bronze | 4.4 K & 1.9 K | March 2007 FNAL |
| TQS02a | RRP 54/61 (2800 A/mm ²) | 20, 21, 22, 23 | Titanium | 4.4 K & 1.9 K | June 2007 FNAL |
| TQS02b | RRP 54/61 | 22, 23, 28,29 | Titanium | 4.4 K & 1.9 K | March 2008 CERN |
| TQS02c | RRP 54/61 | 22, 23,28,20 | Titanium | 4.4 K & 1.9 K | June and Sept. 2008 CERN |
| TQS02d | RRP 54/61 | 22, 23,28,20 | Titanium | 4.4 K & 1.9 K | Dec. 2008 CERN |
| TQS03a | RRP 108/127 | 30, 31, 32, 33 | Titanium | 4.4 K & 1.9 K | Summer 2009 CERN |



LARP

TQS02a, TQS02b and TQS02c Training

TQS02a (20, 21, 22, 23)

FNAL

ϵ_θ from 1370 to 1600 $\mu\epsilon$ \downarrow ϵ_z from 1100 to 1500 $\mu\epsilon$

TQS02b (28, 29, 22, 23)


CERN


Limitation by coil 29

Coil 29 replaced
by coil 20 \downarrow

TQS02c (28, 20, 22, 23)


CERN

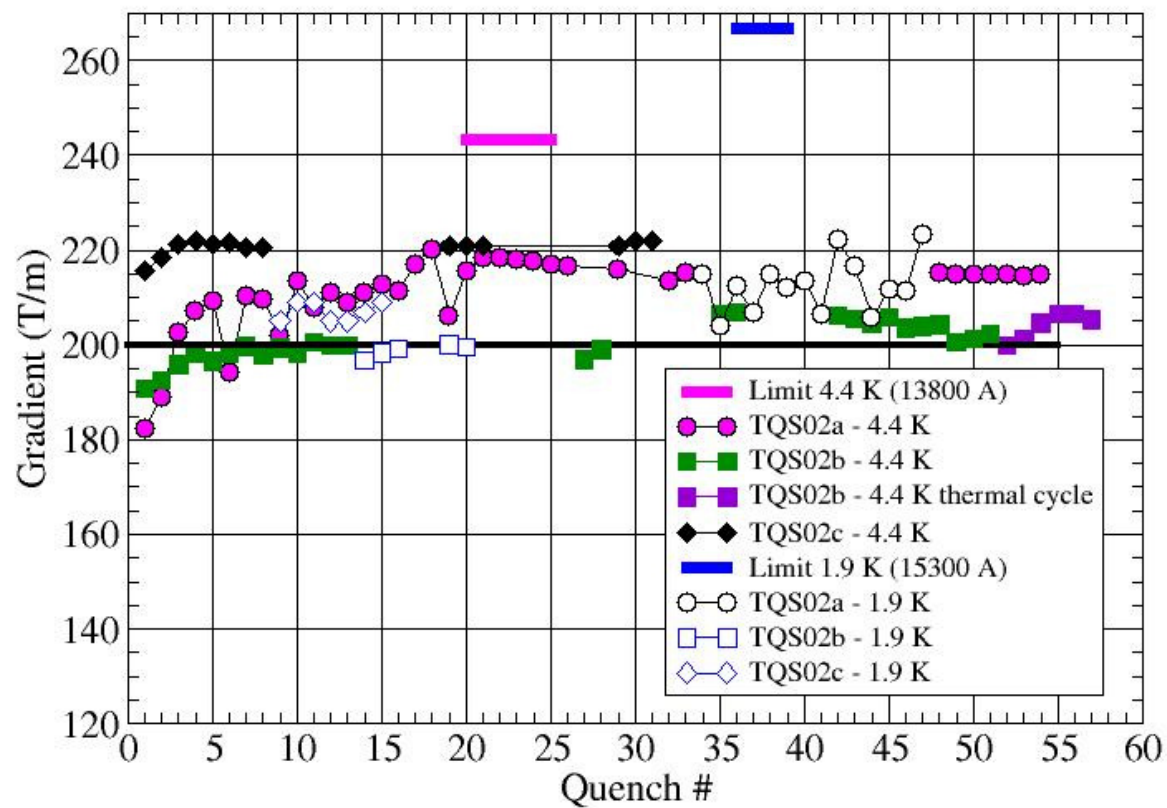




LARP

TQS02c Thermal Cycles – 4.4 K and 1.9 K Trainings

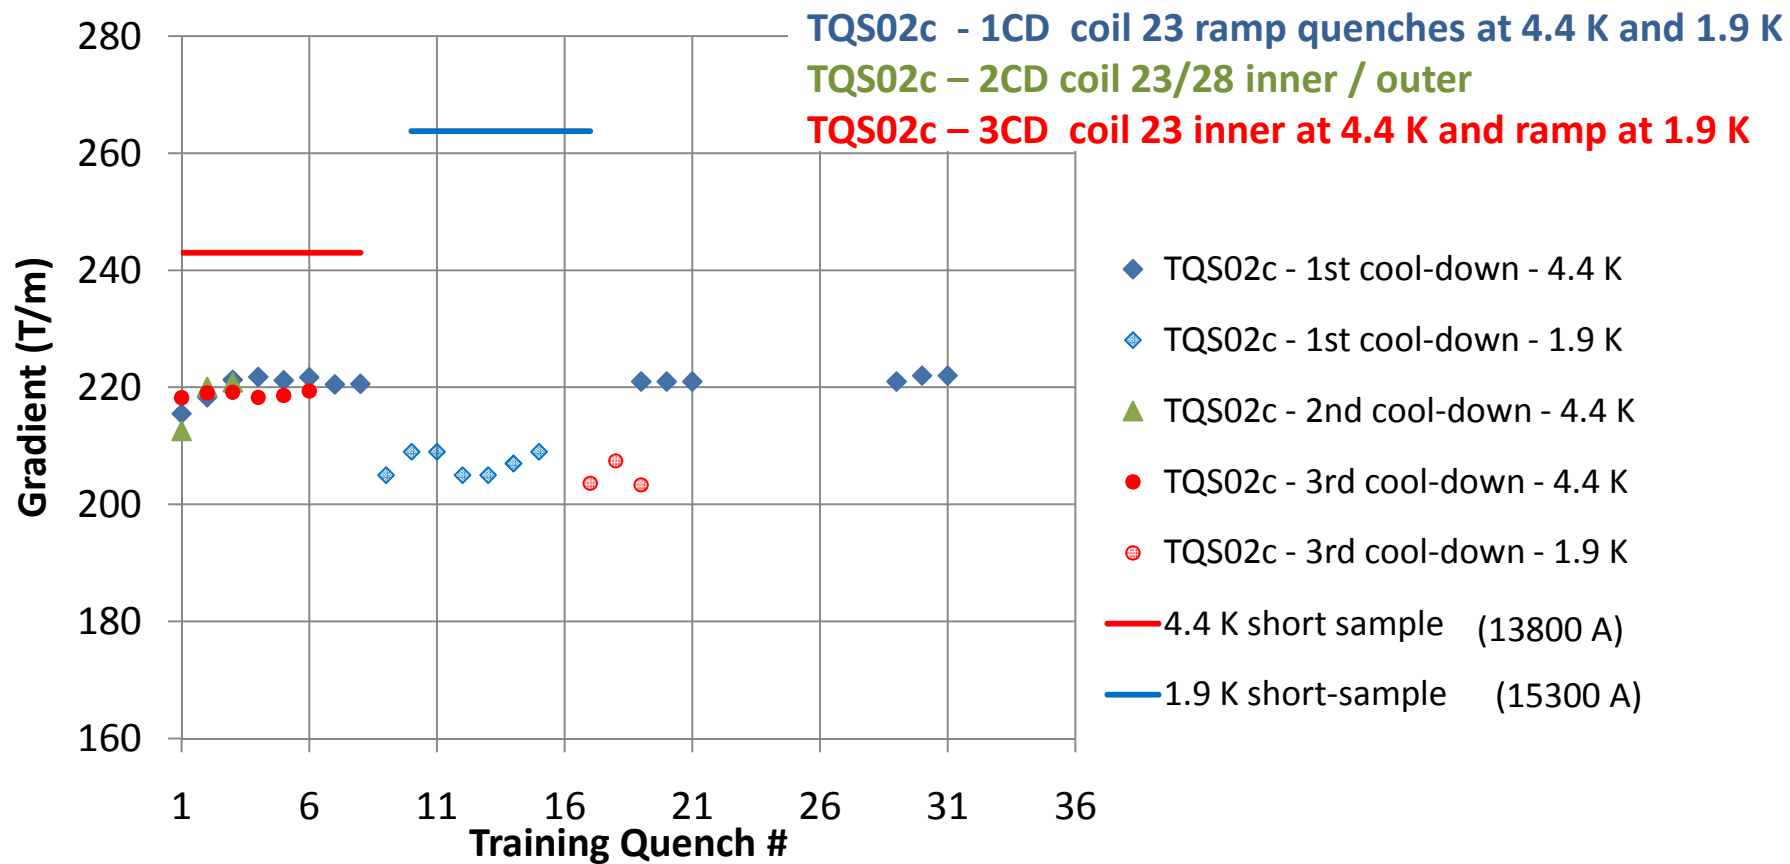


1.9 K tests confirm the instable behavior observed in TQS02a and b

Similar quench location at 4.4 K and 1.9 K




LARP

TQS02c - Ramp rate

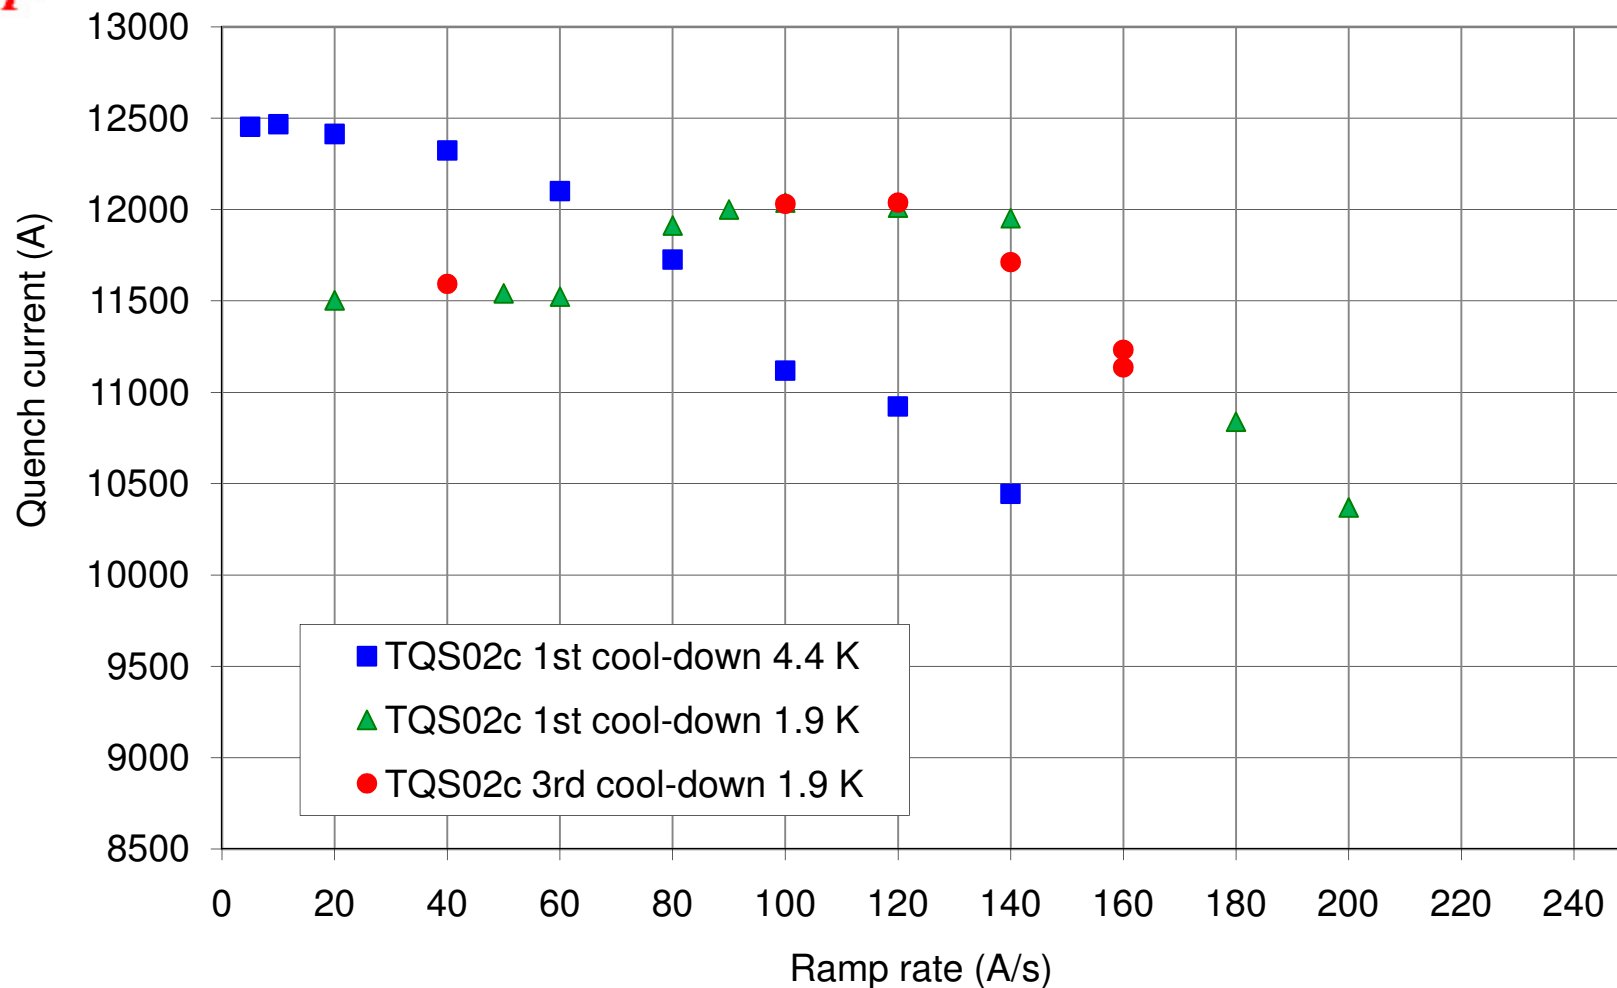

1.9 K ramp rate dependence inversion confirmed by TQS02c third cool-down





LARP

TQS02d


No complete disassembly
 ⇔ Thermal cycle with reduced end loading
 Juan Carlos Perez CERN
 Ray Hafalia LBNL

Steel bars preventing the end plate from axially fully preloading the coils

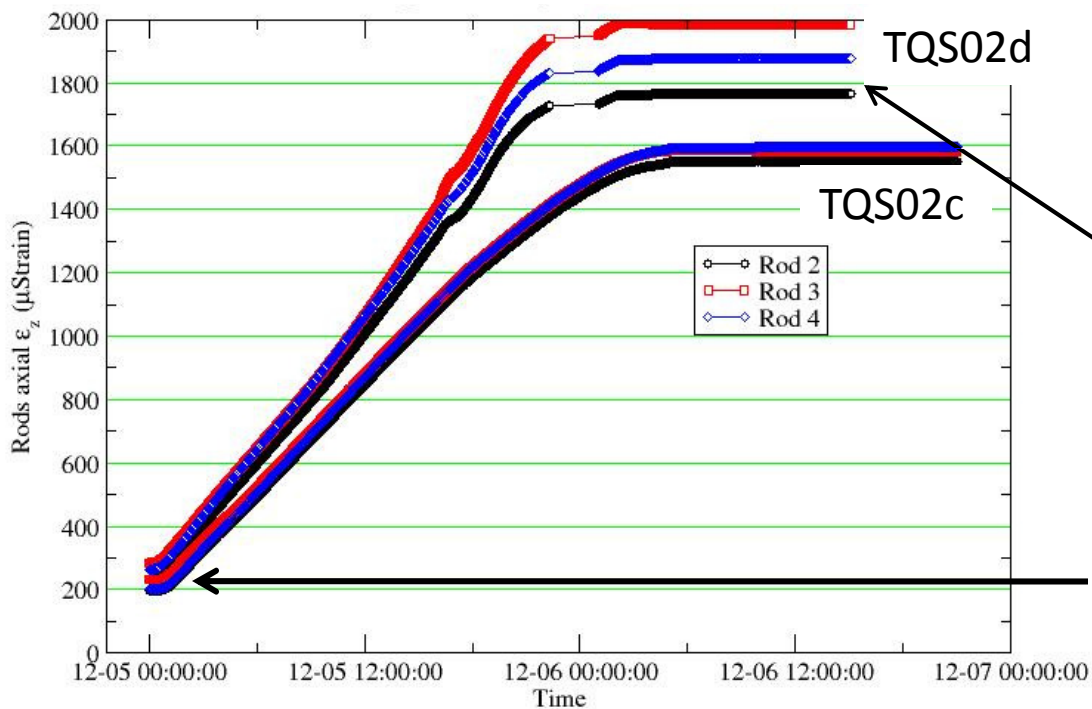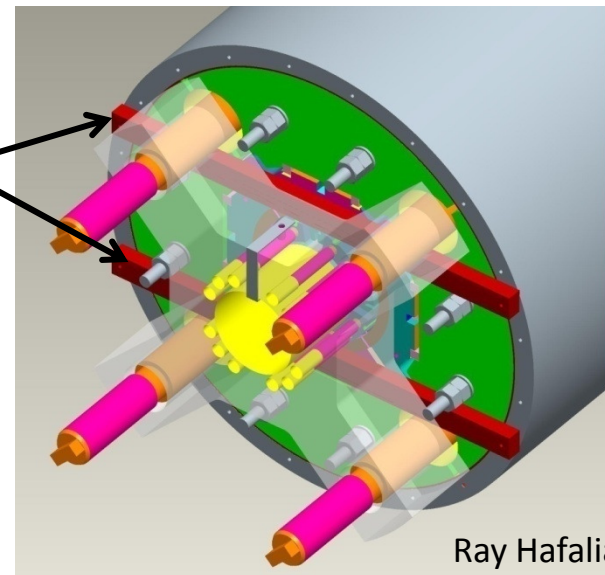


Increase of axial tension in the rods during cool-down
 ⇒ plate pushing against a low thermal contraction part


Same room temperature axial loading



LARP

TQS02c – TQS02d training

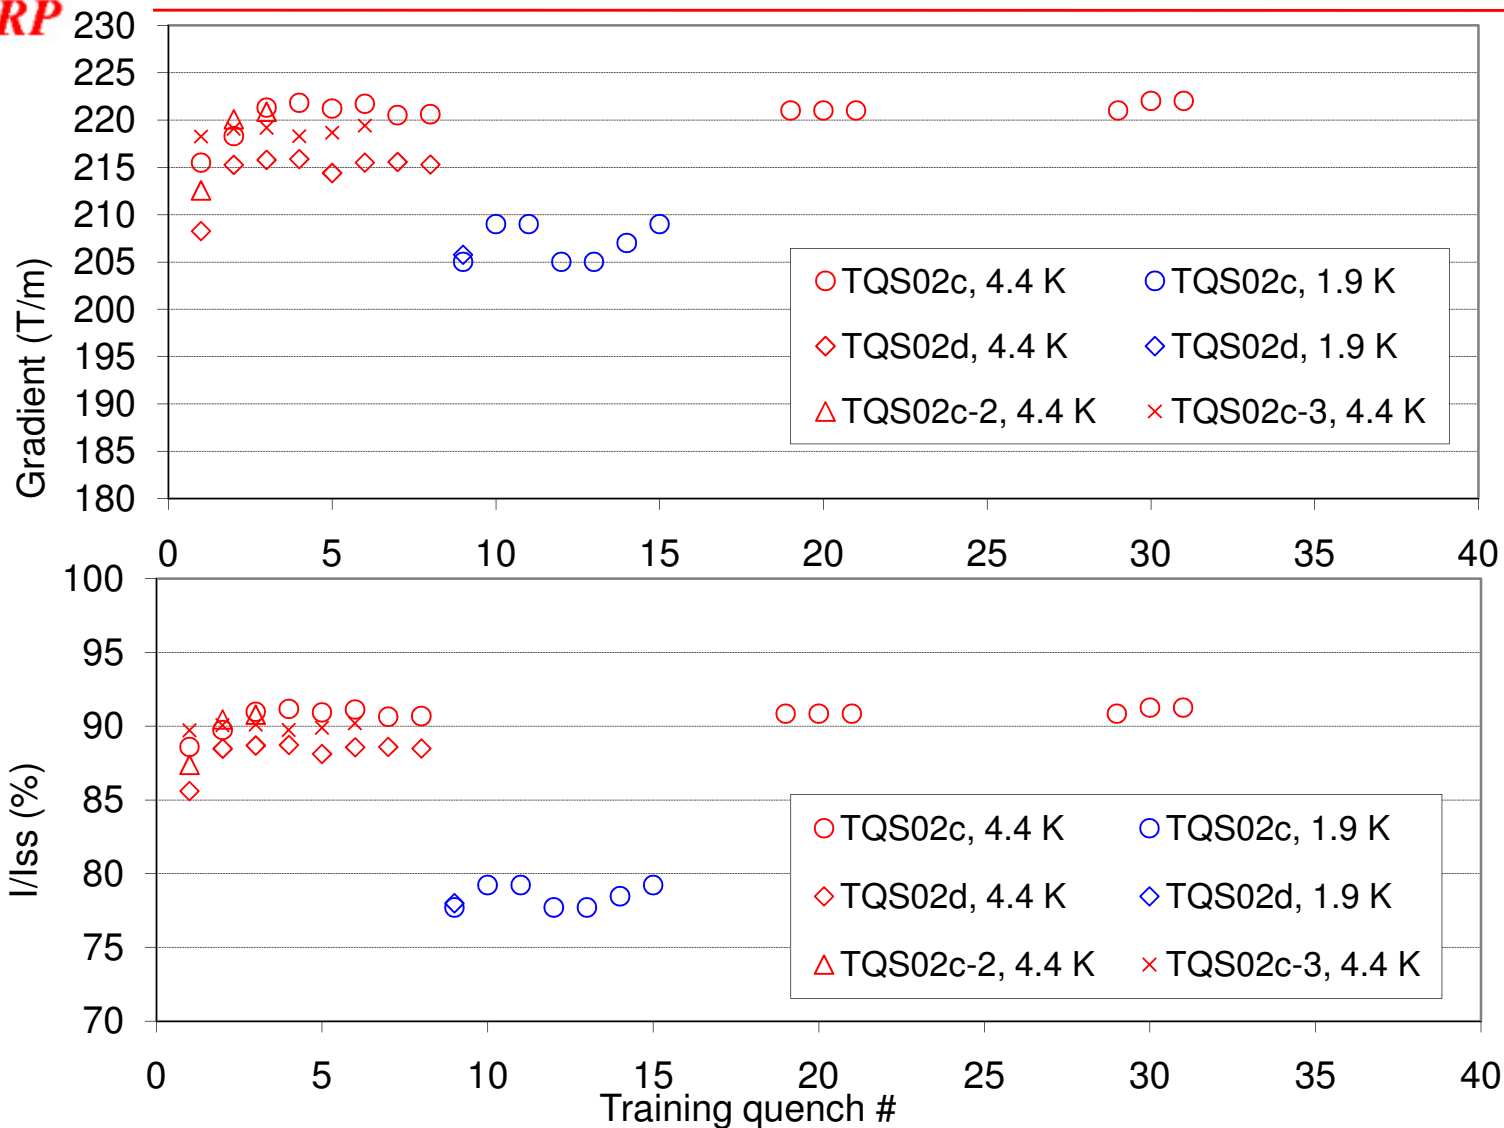



LARP

Instability tests performed on TQS02c and TQS02d

Test plan prepared by B. Bordini (CERN), M. Bajko (CERN), S. Caspi and H. Felice
Based on B. Bordini's work on instabilities: modeling and strand measurement

Objectives: to understand the influence of the transport current distribution on magnet performances


Strand experiment performed on an RRP strand 54/61 by B. Bordini:

- Current hold at 1350 A at 4.3 K and 6 T → quench at 2.14 K
- Ramping at 2.14 K: quench current = 1050 A

- Current hold at 1200 A at 3.2 K and 6 T → to 1.9 K, quench when ramping
- Ramping at 1.9 K: quench current = 1000 A

- Current hold at 1250 A at 4.3 K and 6 T → to 1.9 K, quench when ramping

The objective was to perform the same test with the magnet




LARP

TQS02c - Cool-down with constant current

In collaboration with Bernardo Bordini and Marta Bajko

Principle of the experiment:


Ramping at the quench current minus 200 A ~ 12100A

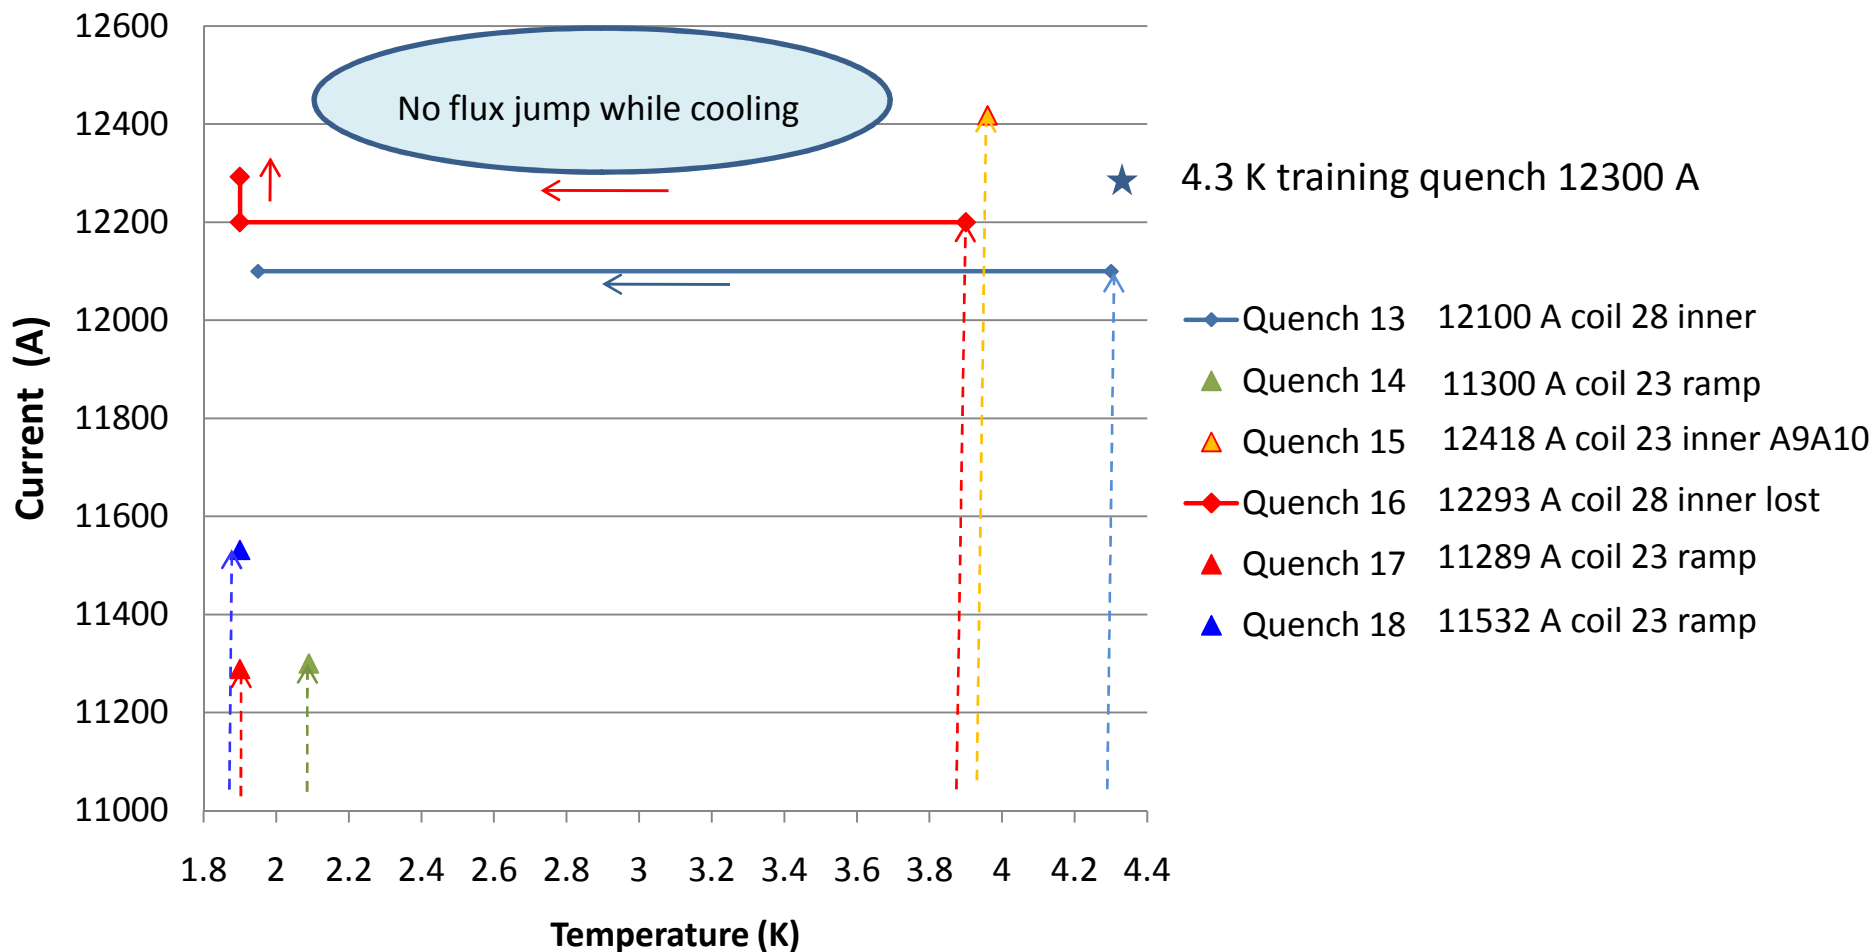



Temperature dependence of TQS02c


In collaboration with Bernardo Bordini and Marta Bajko

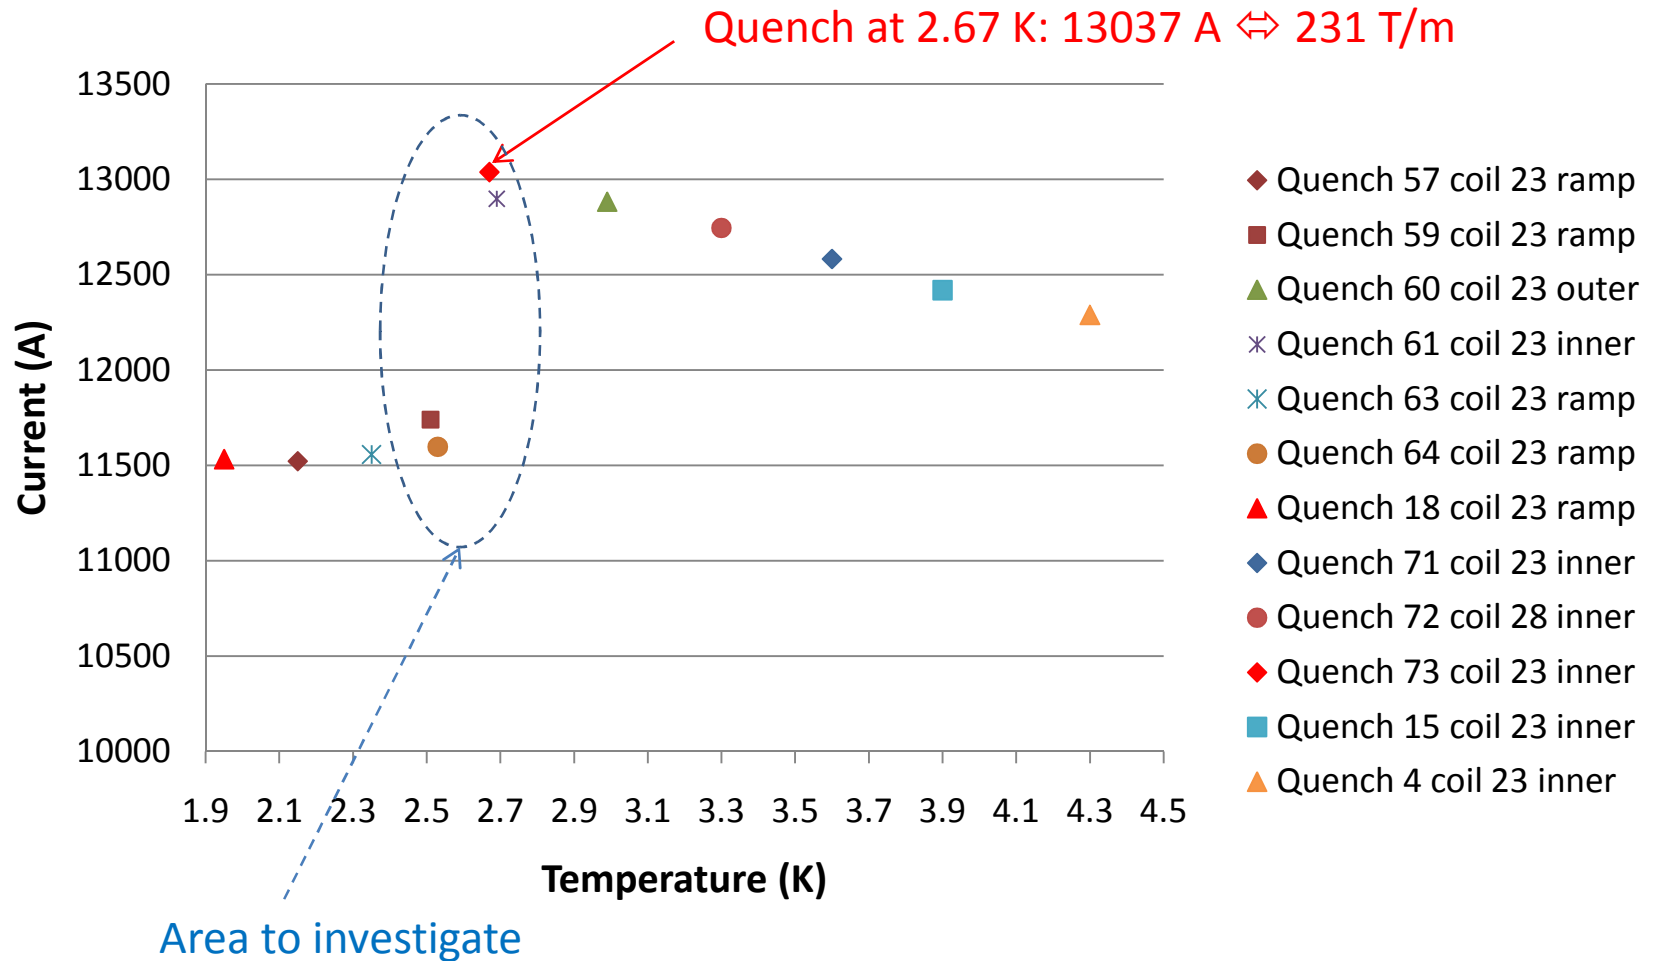




TQS02c and TQS02d Temperature dependence

In collaboration with Bernardo Bordini and Marta Bajko

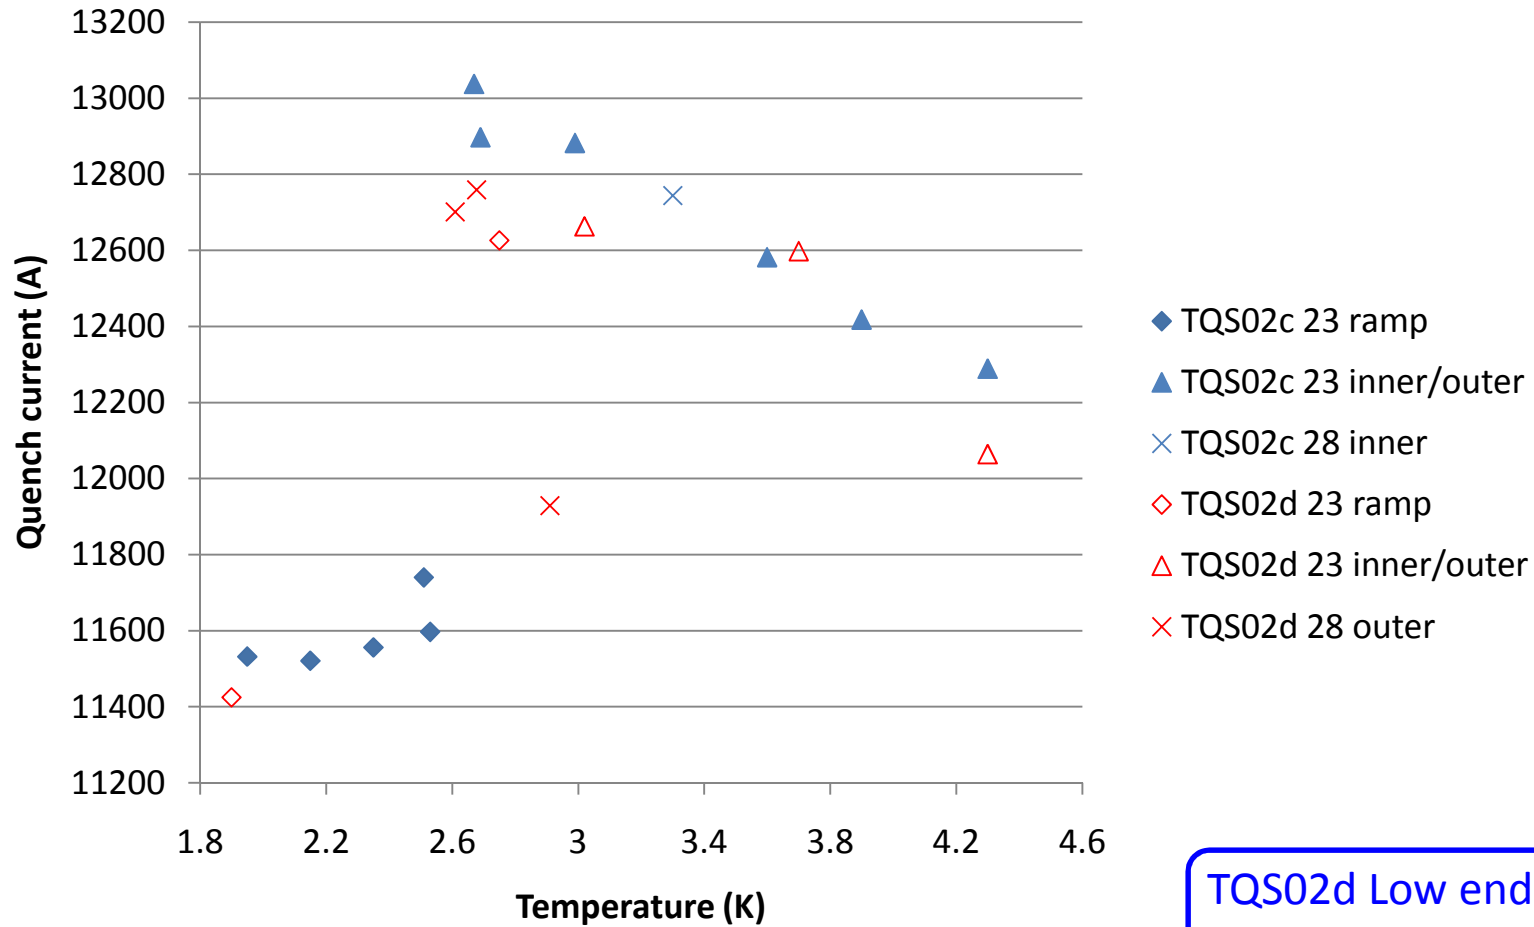


TQS02d Low end loading
Coil 28 possibly training



LARP


Protection Heater study: TQS02c

Coils: 20, 22, 23 with copper cladding => ~ 3.7 ohms per strip

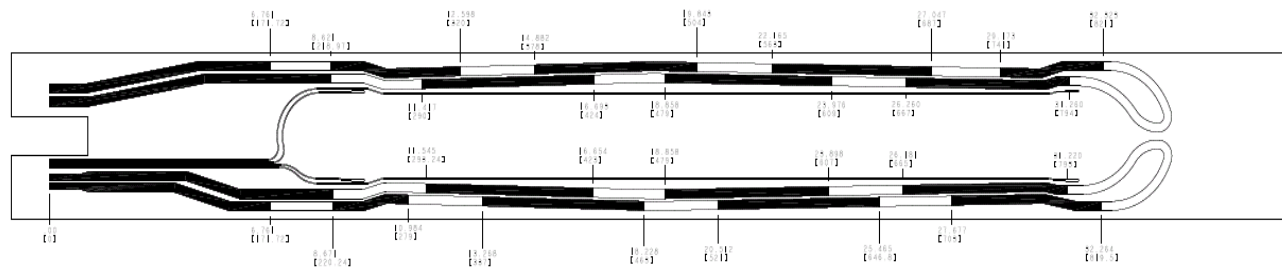


Ray Hafalia

Coil: 28 without copper cladding => ~ 8.7 ohms per strip

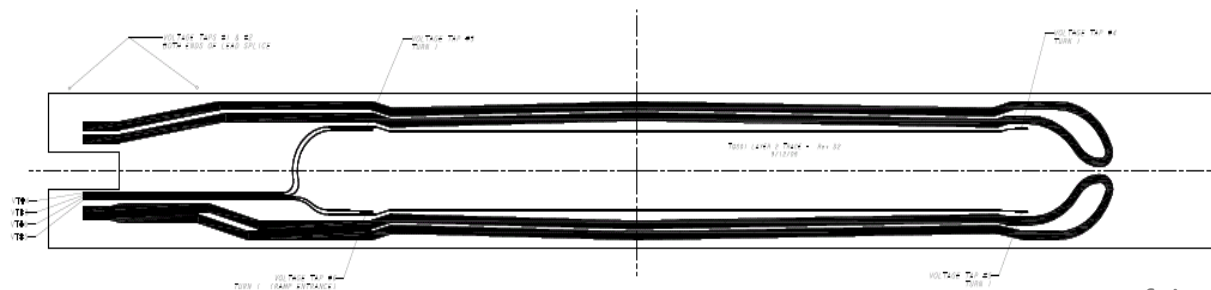

Ray Hafalia





LARP

TQS02c Protection Heater Powering



Test of coil 28 PH
C=4.4 mF $\tau = 31$ ms


PS 1

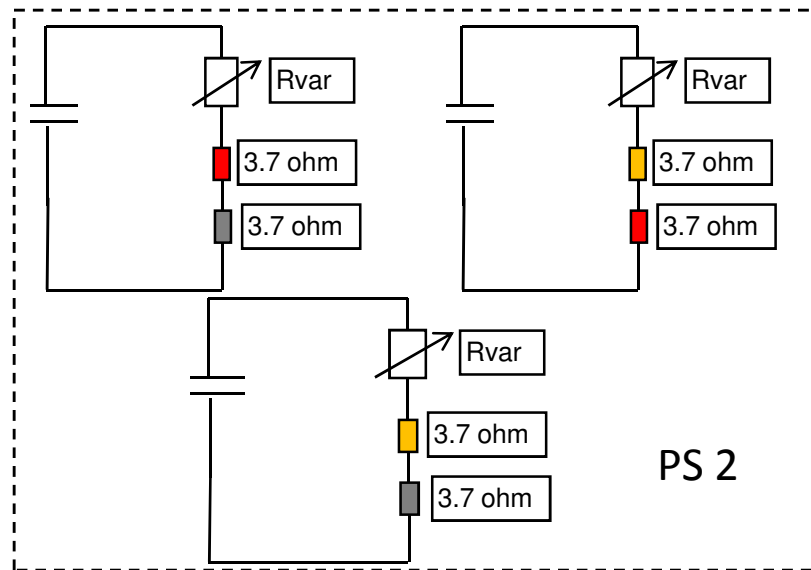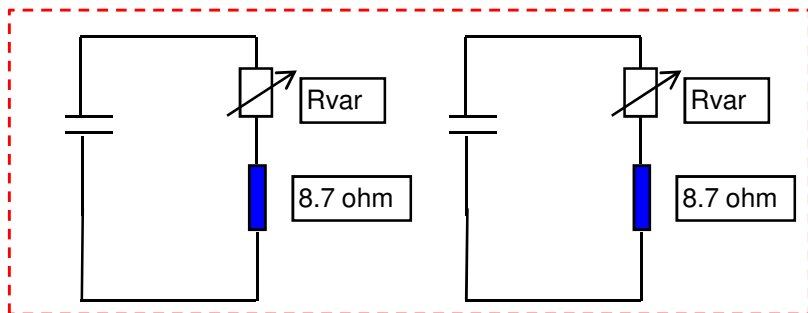

Test of coil 22 PH (CC)
C = 4.4 mF $\tau = 27$ ms

PS 1

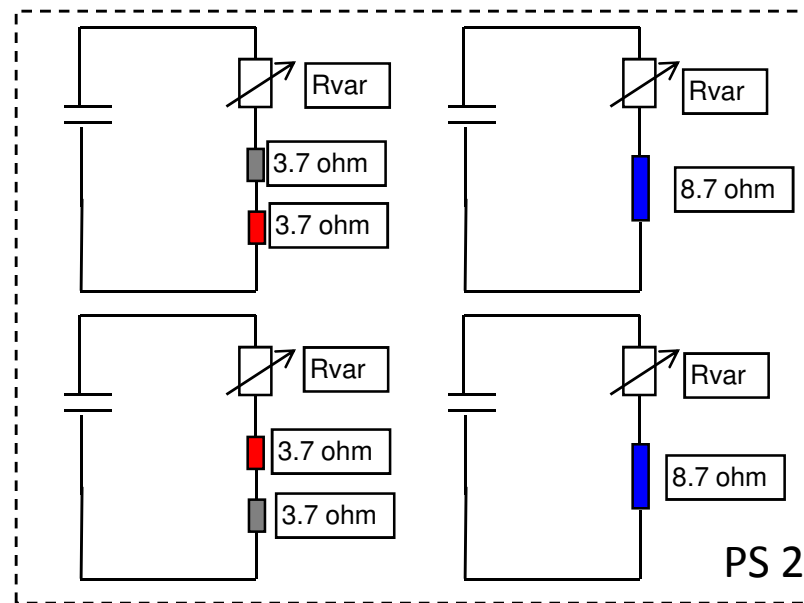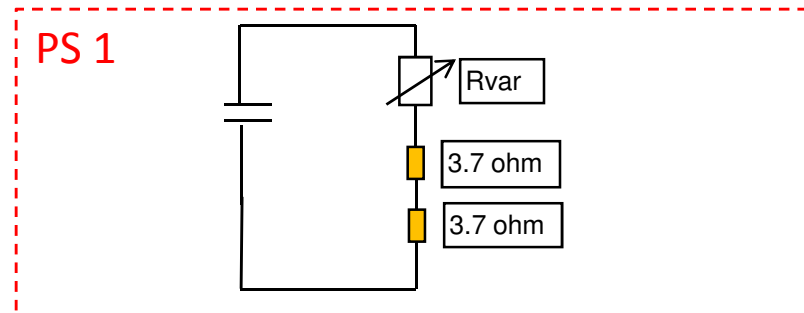





LARP

Delay time versus I magnet

$\tau \sim 30$ ms

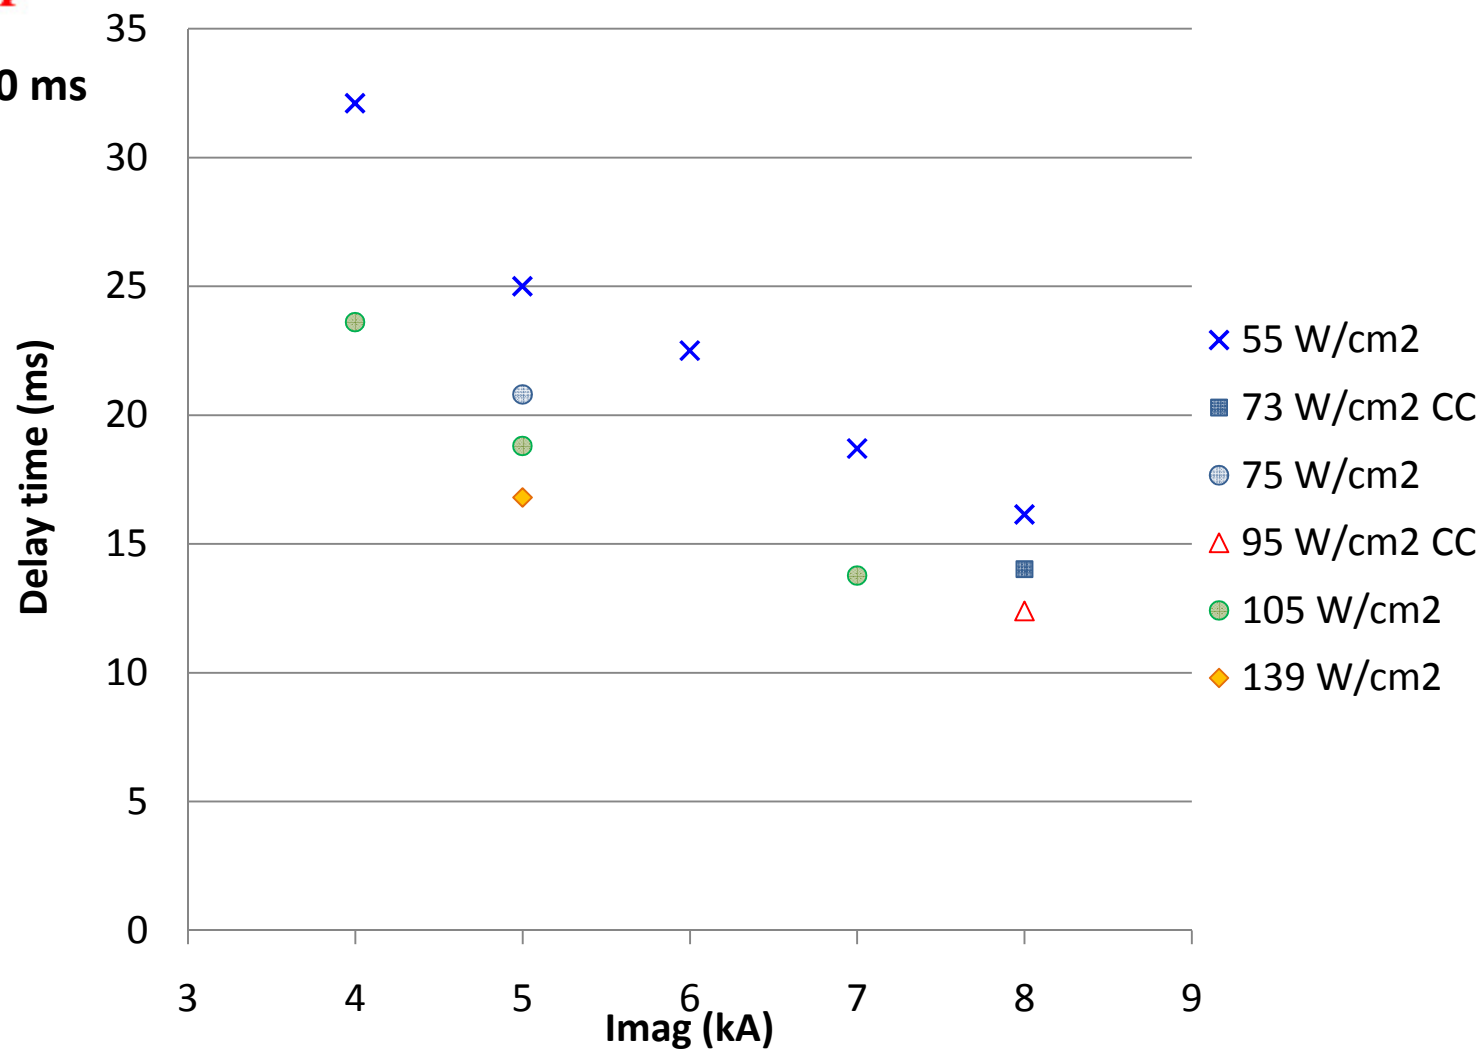





LARP

Delay time versus Power deposition

$\tau \sim 30$ ms

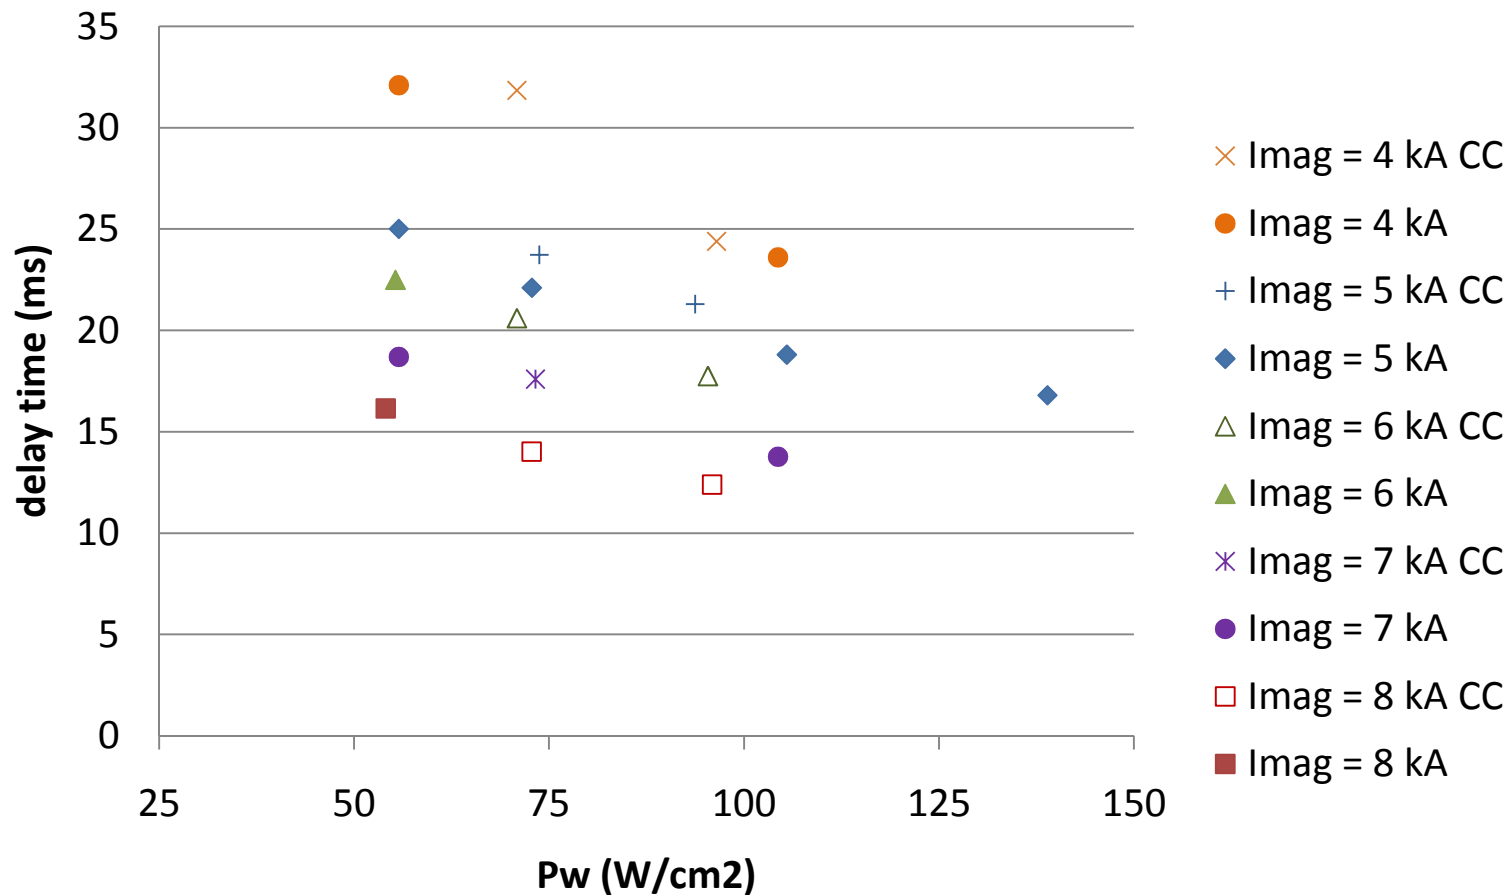





LARP

Comparison with previous tests

$\tau \sim 30$ ms

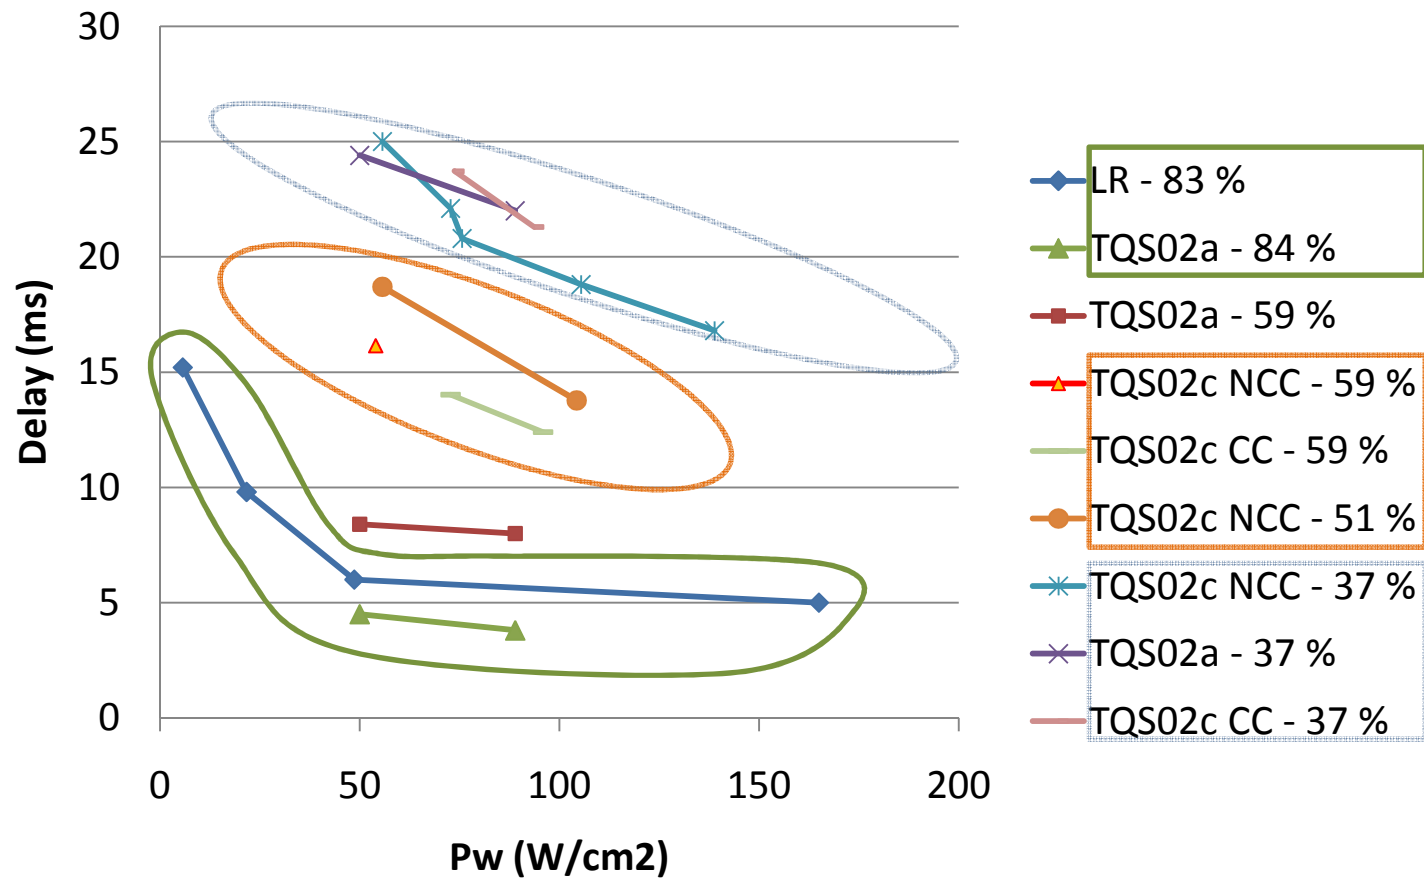



LARP

TQS03

Coils fabrication and instrumentation

- ⇒ 30 and 31 potted, being instrumented
- ⇒ 32 and 33 prepared for potting
- ⇒ 2 types of strain gages wiring
 - ⇒ 30 and 31 with full bridges powered in series
 - ⇒ 32 and 33 with each full bridge powered individually

TQS02d back from CERN and ready to be disassembled

Assembly

Shipping end of May

Test at CERN summer 2009

Test plan

Training / Ramp rate => 108/127 at 4.4 K ad 1.9 K

1.9 K tests => instability?

Protection heater tests

